

3M™ Contrast Enhancement Film (CEF30XXAS Series)

- 3M film CEF3002AS
- 3M film CEF3003AS
- 3M film CEF3004AS
- 3M film CEF3005AS
- 3M film CEF3006AS
- 3M film CEF3008AS



Product Description

3M™ Contrast Enhancement Films (CEF30XXAS Series) are specialized optically clear adhesives offering excellent clarity and adhesion to various transparent display substrates. 3M film CEF30XXAS Series can be used in applications that require soft CEF for filling thick ink step (lens border frame), ITO compatibility and high adhesion. 3M film CEF30XXAS is UV curable and ideal for curved and bent applications.

Product Construction

Product	3M™ film CEF3002AS	3M™ film CEF3003AS	3M™ film CEF3004AS	3M™ film CEF3005AS	3M™ film CEF3006AS	3M™ film CEF3008AS
Adhesive Type:	Acrylic	Acrylic	Acrylic	Acrylic	Acrylic	Acrylic
Adhesive Carrier:	None	None	None	None	None	None
Approximate Thickness:						
Release Liner:	50 µm (2.0 mils) Anti-Static Treated Clear Polyester	50 µm (2.0 mils) Anti-Static Treated Clear Polyester	50 µm (2.0 mils) Anti-Static Treated Clear Polyester	50 µm (2.0 mils) Anti-Static Treated Clear Polyester	50 µm (2.0 mils) Anti-Static Treated Clear Polyester	50 µm (2.0 mils) Anti-Static Treated Clear Polyester
Adhesive:	50 µm (2.0 mils)	75 µm (3.0 mils)	100 µm (4.0 mils)	125 µm (5.0 mils)	150 µm (6.0 mils)	200 µm (8.0 mils)
Release Liner:	75 µm (3.0 mils) Anti-Static Treated Clear Polyester	75 µm (3.0 mils) Anti-Static Treated Clear Polyester	75 µm (3.0 mils) Anti-Static Treated Clear Polyester	75 µm (3.0 mils) Anti-Static Treated Clear Polyester	75 µm (3.0 mils) Anti-Static Treated Clear Polyester	75 µm (3.0 mils) Anti-Static Treated Clear Polyester

Note: 3M film CEF30XX is also available without anti-static treated release liner.

3M™ Contrast Enhancement Film (CEF30XXAS Series)

Typical Physical Properties and Performance Characteristics

Note: The following technical information and data should be considered representative or typical only and should not be used for specification purposes. These results may be based on a limited sample size, and your results may vary depending on test types and conditions.

Performance in Certain Environmental Conditions:

The following environmental tests were conducted in the 3M laboratory under the conditions specified without any appreciable deterioration in visible appearance (no bubbles, delamination, etc.). Sample construction is Optical glass/3M film CEF30XXAS/Optical glass, cured 1J/cm².

	Condition	Duration
High Temp/Humidity-1	+65°C/90%RH	800 hours
Thermal Shock	-40°C and +85°C (1 hour dwell, 1 < min ramp time)	200 cycles

Peel Adhesion:

ASTM D3330 modified, 180-degree peel from float glass, 1 cm wide peel strips, 12 in/min (305 mm/min), 2.0 mil polyester backing, 3M film CEF30XXAS cured 1J/cm²

Peel Adhesion to Glass		
Dwell Time	20 min dwell at 23°C/50%RH	3 days dwell at 23°C/50%RH
Units	N/cm	N/cm
3M film CEF3002AS	4.8	7.6
3M film CEF3003AS	8.1	11.2
3M film CEF3004AS	11.2	14.0
3M film CEF3005AS	13.7	16.7
3M film CEF3006AS	15.1	17.4
3M film CEF3008AS	15.5	17.6

Color:

Ultra Scan Pro (Hunter Lab), ASTM E308, D65/10°. 3M film CEF30XXAS on Optical glass, uncured.

3M™ film CEF3002AS	3M™ film CEF3003AS	3M™ film CEF3004AS	3M™ film CEF3005AS	3M™ film CEF3006AS	3M™ film CEF3008AS
L* = 96.9	L* = 96.9	L* = 96.9	L* = 96.9	L* = 96.9	L* = 96.9
a* = 0.03	a* = 0.03	a* = 0.03	a* = 0.03	a* = 0.03	a* = 0.03
b* = 0.18	b* = 0.18	b* = 0.18	b* = 0.18	b* = 0.20	b* = 0.20

3M™ Contrast Enhancement Film (CEF30XXAS Series)

Refractive Index:

(+ 0.0005 Metricon measurements from standard deviation of ellipsometry) 3M film CEF30XXAS Series, uncured and cured at 3J/cm².

3M™ film CEF30XXAS Series			
Wavelength	405 nm	532 nm	633 nm
Uncured	1.4989	1.4862	1.4819
Cured	1.4991	1.4869	1.4818


Haze:

Haze is measured according to ASTM D1003-92. 3M film CEF30XXAS on Optical glass, uncured.

3M™ film CEF3002AS	3M™ film CEF3003AS	3M™ film CEF3004AS	3M™ film CEF3005AS	3M™ film CEF3006AS	3M™ film CEF3008AS
0.1%	0.1%	0.1%	0.1%	0.1%	0.1%

Transmission Curve:

Transmission vs. Wavelength (Corrected for Reflection Loss of LCD) for 3M film CEF30XXAS on Glass

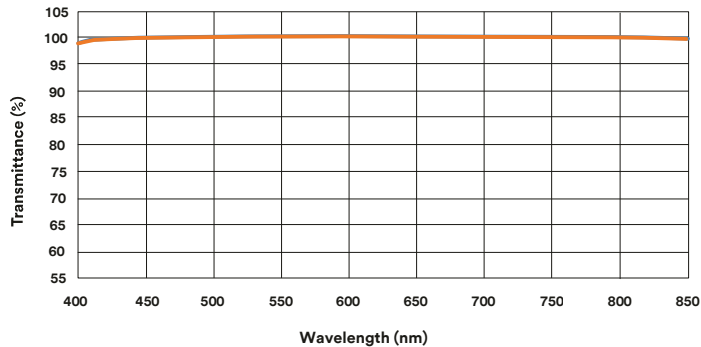

Typical Electrical Properties at Room Temperature:

ASTM-D150-92. 3M film CEF30XXAS cured 3 J/cm²

Dielectric Constant:

3M™ Contrast Enhancement Film CEF30XXAS	
Frequency (kHz)	Dielectric Constant
100	3.44
500	3.21

3M™ Contrast Enhancement Film (CEF30XXAS Series)

Suggested Lamination Process

Step 1: Remove secondary liner, then laminate 3M film CEF30XXAS to first adherent substrate by roller at room temperature


Recommendation: roller pressure 0.1 – 0.2 MPa, roller speed 0.5 – 1 m/min

Step 2: Remove primary liner, then laminate 3M film CEF30XXAS/first adherent to second adherent by vacuum lamination Recommendation: Vacuum condition < 50 Pa, pressure around 0.1 – 0.2 MPa

Step 3: Autoclave process

Recommendation: 30-60°C/3-5kgf/cm²/20-30min

Step 4: UV curing with minimum 1J/cm² dosage (UVA)

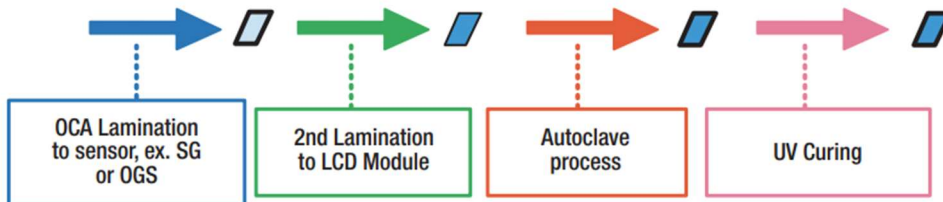

UV Cure Guidance

- UV range: 340-375nm (max absorption = 342nm)
- Minimum UV dosage and intensity: 1 J/cm², 10 mW/cm²
- Suggest using lower wavelengths of the UV-A spectra
- UV source options would be Fusion D bulb and med pressure Hg
- LED sources, which output at longer UV-A wavelengths would be less ideal

Storage

- Avoid applying pressure or resting objects on the product to prevent marking, denting, or deforming the surface
- Wear gloves to prevent fingerprints or nail marks when handling
- Product needs to be unpacked and handled in the clean-room facility
- Product must be protected from light exposure
- Store in sealed, foil bag under -20°C to 30°C and less than 70% relative humidity. If removed from cold storage, ensure no condensation on packaging

Regulatory: For regulatory information about this product, contact your 3M representative.

3M™ Contrast Enhancement Film (CEF30XXAS Series)

Technical Information: The technical information, guidance, and other statements contained in this document or otherwise provided by 3M are based upon records, tests, or experience that 3M believes to be reliable, but the accuracy, completeness, and representative nature of such information is not guaranteed. Such information is intended for people with knowledge and technical skills sufficient to assess and apply their own informed judgment to the information. No license under any 3M or third party intellectual property rights is granted or implied with this information.

Product Use: Many factors beyond 3M's control and uniquely within user's knowledge and control can affect the use and performance of a 3M product in a particular application. As a result, customer is solely responsible for evaluating the product and determining whether it is appropriate and suitable for customer's application, including conducting a workplace hazard assessment and reviewing all applicable regulations and standards (e.g., OSHA, ANSI, etc.). Failure to properly evaluate, select, and use a 3M product in accordance with all applicable instructions and with appropriate safety equipment, or to meet all applicable safety regulations, may result in injury, sickness, death, and/or harm to property.

Warranty, Limited Remedy, and Disclaimer: Unless a different warranty is specifically stated on the applicable 3M product packaging or product literature (in which case such warranty governs), 3M warrants that each 3M product meets the applicable 3M product specifications on the Certificate of Analysis, which is established when the product is manufactured and deemed commercially available and is provided at the time 3M ships the product. **3M MAKES NO OTHER WARRANTIES OR CONDITIONS, EXPRESS OR IMPLIED, INCLUDING, BUT NOT LIMITED TO, ANY IMPLIED WARRANTY OR CONDITION OF MERCHANTABILITY, FITNESS FOR A PARTICULAR PURPOSE, OR ANY IMPLIED WARRANTY OR CONDITION ARISING OUT OF A COURSE OF DEALING, CUSTOM, OR USAGE OF TRADE.** If a 3M product does not conform to this warranty, then the sole and exclusive remedy is, at 3M's option, replacement or repair of the 3M product or refund of the purchase price.

Limitation of Liability: Except for the limited remedy stated above, and except to the extent prohibited by applicable law, 3M will not be liable for any loss or damage arising from or related to the 3M product, whether direct, indirect, special, incidental, or consequential (including, but not limited to, lost profits or business opportunity), regardless of the legal or equitable theory asserted, including, but not limited to, warranty, contract, negligence, or strict liability.

Disclaimer: For industrial use only. Not intended, labeled or packaged for consumer sale or use.



3M Display & Electronics
3M Center, Building 223-3S-32
St. Paul, MN 55144-1000 U.S.A.

Phone 1-800-3M HELPS
Web 3M.com/oca

3M is a trademark of 3M Company.
All other trademarks herein are the
property of their respective owners.
©3M 2025. All rights reserved.
60-5005-0562-7