

Development of a New Cartridge Filter for
Significantly Improved Wine Microbiological Stability

Thomas O'Brien, Ph.D.
Senior Applications Specialist, Scientific Applications Support Services

Conor O'Hara, BS, MBA
Director of Marketing - Worldwide, Food & Beverage

Poster Presented at the 2006 Unified Wine & Grape Symposium
Sacramento, CA January 22, 2006

Abstract

Controlling spoilage microorganisms prior to packaging is critical for wine production. Eliminating these spoilage organisms without affecting the other wine properties is of vital importance to producing a consistent, high quality wine. Installation of final membrane filters into the production process provides the means to control and eliminate spoilage organisms in the finished wine. Of equal importance is attaining long on-stream filter service life to minimize the operating costs associated with installation of filters into the production line.

3M Purification Inc. initiated a project to develop a robust, highly microorganism retentive final filter that would withstand the rigorous cleaning and sanitation regimens employed by most wine producers. The highly durable membrane and cartridge design withstands repeated exposure to hot water sanitation, steam sterilization and industry common chemical cleaning and sanitizing agents. This filter also delivers the performance required by the wine industry. The new membrane filter design delivers an increased product flow rate at a lower pressure drop across the filters that results in the installation of smaller filter assemblies, thus lowering the overall operational costs.

This poster reports on the development of a new membrane final filter whose construction is optimized to increase product throughput. This results in a reduction in the number of installed filters, avoiding the need to increase the filtration system footprint size, thereby, reducing the impact of filtration costs. LifeASSURE™ BNA and BDA series membrane filter design employs a new highly-asymmetric polyether sulfone membrane, an upstream and downstream support design that delivers excellent spoilage organism retention with minimal impact on the organoleptic properties of the finished wine.

Laboratory and actual customer field data are presented from bench-scale filtration studies to the results from production line trials.

Materials of Construction

The filters employed in this study were manufactured by 3M Purification. The filter media is a new single-layer, highly-asymmetric polyether sulfone (PES) membrane.

As shown in the membrane cross-section in Figure 1, the upstream pores are very open to provide both pre-filtration and retention. The downstream pores are tighter than the upstream pores and provide retention of the spoilage organisms. The asymmetric design allows larger particles, colloids and spoilage organisms to be trapped by the larger upstream pores, preventing these contaminants from fouling or blinding-off the tighter downstream pores. The finer downstream pore structure then traps finer particulates, cell debris and haze components. In this design, the effective depth of penetration and entrapment of microorganisms and particles is increased (greater contaminant capacity) as compared to a conventional uniform pore size membrane filters, resulting in increased fluid throughput without sacrificing filtrate quality.

PES is highly durable and extremely resistant to typical cleaning and sanitization agents used in the Wine Industry.

LifeASSURE BNA and BDA series filter cartridges are constructed by pleating the highly asymmetric PES membrane with polypropylene upstream and downstream membrane cross section. Magnification 2500X support materials. The core, cage and end cap adapters are made of polypropylene. The media, support materials and cartridge components are thermally sealed. No resin or binder compounds are added. Multiple length cartridges with industry standard connection styles are produced to fit the most widely used housing designs.

As shown in Figure 2, the media and support materials are fabricated into the cartridge pleat pack with the Advance Pleat Technology (APT) design. This design provides greater service life and faster flow rates than other media designs. The variation in pleat height maintains open flow paths between pleats. The design maximizes access by contaminants to the available filtration surface area thus increasing the contaminant holding capacity of each cartridge. The pleats are well separated at the cartridge core, reducing the resistance to fluid flow resulting in a lower pressure drop across the cartridge. The combination of a lower pressure drop across the cartridge and the maximum available filtration surface area leads to longer service life, faster flow rates and improved filtration economics.

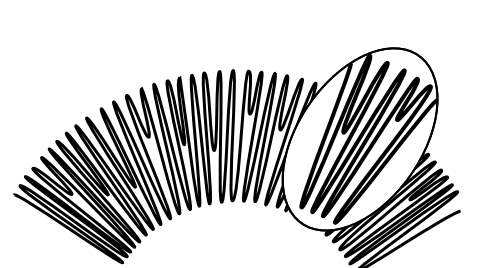


Figure 2. Graphic representation of the Advanced Pleat Technology membrane pleating design.

Cartridges are available in both 0.45 μm and 0.65 μm retention ratings and were specifically developed and tested for Food and Beverage applications as final filters to control spoilage organisms.

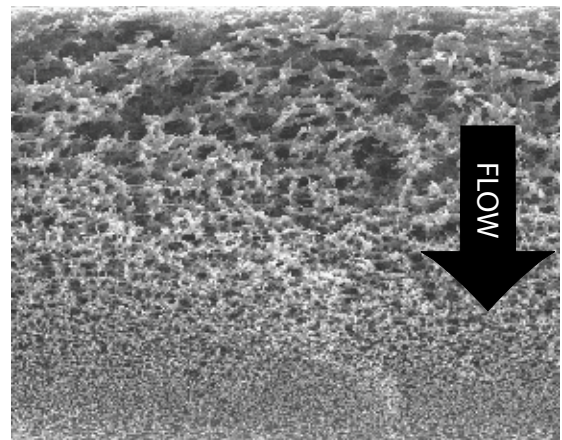


Figure 1. Scanning electron micrograph of PES membrane cross section. Magnification 2500X

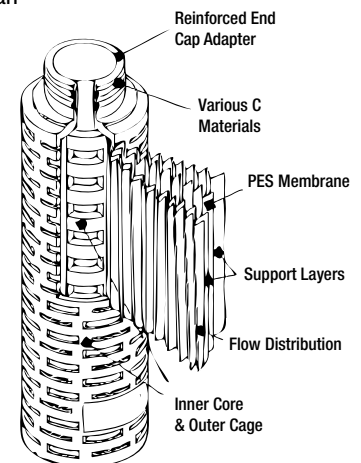



Figure 3. LifeASSURE™ BNA and BDA series filter cartridge components and construction.

Laboratory Based Product Performance Test Results

Service Life

LifeASSURE™ BNA and BDA series filters and alternative membrane filters used in wine filtration, all rated at 0.45 µm, were flushed with water at 3 gpm for 5 minutes with a 5 psi back pressure and forward flow integrity tested. The cartridges were then challenged at a constant flow rate of 3 gpm with an aqueous suspension of particulates, colloids, and complex carbohydrates common to the Food and Beverage industry. The test is designed to simulate beverage filtration at an accelerated rate. The throughput was measured in gallons until a terminal differential pressure of 15 psid above the clean pressure drop across the cartridge was reached, indicating the filters were plugged.

Graph 1. Relative Service Life of Comparable 0.45 micron Rated Membrane Filters Using Surrogate Plugging Mixture

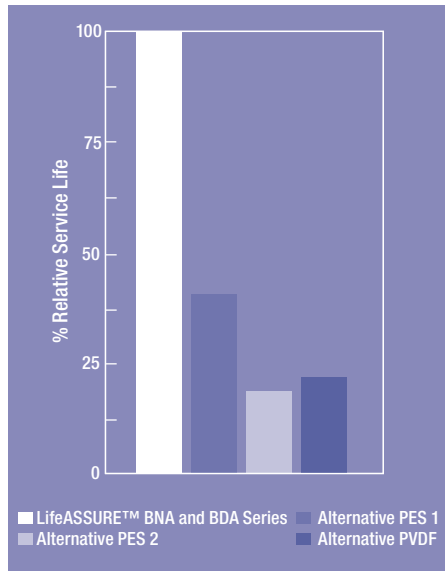

The alternative filters tested were commercially available membrane filters commonly used in wine filtration. Two of the filters were constructed with alternative polyether sulfone (PES) membranes and one contained a polyvinylidene fluoride (PVDF) membrane.

Results: LifeASSURE BNA and BDA series filter cartridges demonstrated greater than twice the service life, as expressed in the number of gallons processed prior to filter plugging, of the nearest alternative BNA and BDA cartridge.

Microorganism Retention Basis of Tests

The primary purpose of a membrane filter installed in a food or beverage process is to effectively control spoilage microorganisms. Microorganisms specific to the food and beverage industry were selected to demonstrate the retention capabilities of LifeASSURE BNA and BDA series filter cartridges.

Procedure

LifeASSURE BNA and BDA series 10 inch cartridges rated 0.45 µm and 0.65 µm from three different production lots were flushed with water at 3 gpm for 5 minutes with a 5 psi back pressure then forward flow integrity tested. The cartridges were then challenged with a suspension of the selected organism in an appropriate carrier fluid at concentrations ranging from 1 x 10⁶ CFU/mL to 1 x 10⁷ CFU/mL. The filtrate from each cartridge was assayed to determine the log reduction ratio value (LRV) for each cartridge. Post-challenge, the cartridges were flushed with deionized water and forward flow integrity tested to confirm they were still integral after the bacteria challenge.

The challenge organisms tested were:

Oenococcus oeni suspended in white wine, *Serratia marcescens* suspended in sterile deionized water, *Lactobacillus brevis* suspended in degassed beer and *Dekkera intermedia* (*Brettanomyces*) suspended in dilute acetic acid solution at pH 4.0.

Table 1 – Summary of Microorganism Retention Testing

| LifeASSURE™ BNA and BDA series | Microorganism | Typical Log Reduction Value (LRV) |
|--------------------------------|-----------------------------|-----------------------------------|
| BNA045 | <i>Serratia marcescens</i> | 8 |
| BNA045 | <i>Oenococcus oeni</i> | 9 |
| BNA045 | <i>Lactobacillus brevis</i> | 10 |
| BNA045 | <i>Dekkera intermedia</i> | 9 |
| BNA065 | <i>Lactobacillus brevis</i> | 7 |
| BNA065 | <i>Dekkera intermedia</i> | 9 |

Log Reduction Values are calculated using the following formula:

$$LRV = \log_{10} \left(\frac{\text{total number of organisms entering the filter}}{\text{total number of organisms exiting the filter}} \right)$$

Exposure to Hot Water and Steam

In order to evaluate the effects of thermal stress, LifeASSURE™ BNA and BDA series 10-inch cartridges from different production lots were subjected to repetitive Hot Water (90°C) and in-situ steam cycles at 135°C. The hot water and in-situ steam cycles were 30 minutes each with cooling between cycles. Test filters were evaluated for integrity by Forward Flow Integrity Testing (FFIT) at a test pressure of 22 psi or 15 psi for 0.45 µm rated and 0.65 µm rated, respectively, initially and at various intervals following the thermal cycles.

Table 2 – The Effect of Thermal Stress on LifeASSURE™ BNA and BDA Series Cartridges

| Treatment | Grade | Cartridge Serial Number | Integrity Test Results | | |
|---------------------------------------|-------------|-------------------------|------------------------|------------|------------|
| | | | 50 Cycles | 100 Cycles | 150 Cycles |
| Hot Water 194°F/90°C 30 minutes | 0.45 µm | 05N020-0007 | Pass | Pass | Pass |
| | | 05N020-0020 | Pass | Pass | Pass |
| | | 05N020-0029 | Pass | Pass | Pass |
| | | 05N024-0005 | Pass | Pass | Pass |
| | | 05N024-0012 | Pass | Pass | Pass |
| | | 05N024-0019 | Pass | Pass | Pass |
| | | 05N033-0001 | Pass | Pass | Pass |
| | 05N033-0009 | Pass | Pass | Pass | |
| | 05N033-0027 | Pass | Pass | Pass | |
| | 0.65 µm | 05N016-0004 | Pass | Pass | Pass |
| | | 05N016-0015 | Pass | Pass | Pass |
| | | 05N016-0041 | Pass | Pass | Pass |
| | | 05N023-0004 | Pass | Pass | Pass |
| | | 05N023-0013 | Pass | Pass | Pass |
| | | 05N023-0020 | Pass | Pass | Pass |
| | | 05N037-0006 | Pass | Pass | Pass |
| | | 05N037-0019 | Pass | Pass | Pass |
| 05N037-0034 | | Pass | Pass | Pass | |
| | | | | 75 Cycles | 100 Cycles |
| Steam 275°F/135°C, 30 minutes | 0.45 µm | 05N020-0002 | Pass | Fail | N/A |
| | | 05N020-0015 | Pass | Pass | Pass |
| | | 05N020-0025 | Pass | Pass | Pass |
| | | 05N024-0021 | Pass | Pass | Pass |
| | | 05N024-0025 | Pass | Pass | Pass |
| | | 05N024-0045 | Pass | Pass | Pass |
| | | 05N033-0003 | Pass | Pass | Pass |
| | | 05N033-0017 | Pass | Pass | Pass |
| | 05N033-0025 | Pass | Pass | Pass | |
| | 0.65 µm | 05N016-0001 | Pass | Pass | Pass |
| | | 05N016-0008 | Pass | Pass | Pass |
| | | 05N016-0034 | Pass | Pass | Pass |
| | | 05N023-0003 | Pass | Pass | Pass |
| | | 05N023-0012 | Pass | Pass | Pass |
| | | 05N023-0018 | Pass | Pass | Pass |
| | | 05N037-0011 | Pass | Pass | Pass |
| | | 05N037-0029 | Pass | Pass | Pass |
| 05N037-0050 | | Pass | Pass | Pass | |

Sanitation Agent Compatibility – Oxonia Active¹

In order to evaluate the compatibility of LifeASSURE™ BNA and BDA series filter cartridges with peracetic acid/hydrogen peroxide sanitation agents typically used in the Food and Beverage industry, LifeASSURE BNA and BDA series 10-inch cartridges from different production lots were subjected to repetitive exposures to a 1% aqueous solution of Oxonia Active at ambient temperature. Initially, and prior to each exposure interval, the cartridges were forward flow integrity tested at a test pressure of 22 psi or 15 psi for 0.45 µm rated and 0.65 µm rated, respectively. After each exposure interval, the cartridges were forward flow integrity tested to confirm the cartridges remained integral after exposure to the Oxonia Active solution. Following the forward flow integrity testing, each cartridge was forward flow bubble point tested to release as much water as possible from the pores of the membrane and then exposed to a fresh 1% aqueous Oxonia Active solution for the next exposure interval.

Cleaning Agent Compatibility – Sodium Hydroxide

In order to evaluate the compatibility of LifeASSURE BNA and BDA series filter cartridges with caustic cleaning solutions, LifeASSURE BNA and BDA series 10-inch cartridges from different production lots were subjected to repetitive exposures to 1 M aqueous sodium hydroxide (NaOH) solution at 65°C. Initially, and prior to each exposure interval, the cartridges were forward flow integrity tested at a test pressure of 22 psi or 15 psi for 0.45 µm rated and 0.65 µm rated, respectively. After each exposure interval, the cartridges were forward flow integrity tested to confirm the cartridges remained integral after exposure to the 1 M (4% w/v) NaOH solution. Following forward flow integrity testing, each cartridge was forward flow bubble point tested to release as much water as possible from the pores of the membrane and then exposed to a fresh 1 M NaOH solution for the next exposure interval.

Table 3 – Compatibility of LifeASSURE™ BNA and BDA Series Filters to Cleaning and Sanitation Agents

| Treatment | Conditions | Total Number of Hours Tested | Results |
|-------------------------|---|------------------------------|----------------------|
| Oxonia Active | 1% aqueous solution, ambient temperature, continuous soak | 150 | No loss of integrity |
| Sodium Hydroxide (NaOH) | 1 M (4% w/v) aqueous solution, 65°C | 100 | No loss of integrity |

Beta-Site Testing

3M Purification conducts beta-site testing at commercial wineries for all New Products prior to the formal New Product Launch. The purpose of beta-site testing is to collect information from the wineries on whether or not the product as designed meets the winery's performance criteria. Test sites are chosen based on requesting the winery test the New Product in the exact way they would normally use the filter during their production process. Wineries were selected that could meet the following criteria:

1. familiarity with membrane filtration practices and procedures,
2. a stable production schedule and
3. the ability to provide careful monitoring and recording of key filtration data, such as, throughput volume, production flow rate, differential pressure across the filter installation, bacteria retention, integrity test results and the SIP/CIP data (time, temperature, number of cycles, etc.)

3M Purification's Scientific Applications Support Services personnel, a dedicated group of Scientists and Engineers that provide technical support to our Customers, assist the winery in conducting these beta-site tests. The beta-site results are used to confirm whether or not the new product performs as expected under actual field conditions as compared to the internal laboratory testing results obtained during product development.

Chart 5 - Field Beta-Site Testing Results

| Test Site/Wine Filtered | Filter Assembly | Test Site Objectives | Results |
|--|--------------------------------------|---|---|
| California Wine Producer/Red and White Wines | 10 x 30" cartridges 0.45 µm rated | 2 million gallons throughput | Previous alternative filters reportedly processed 1 million gallons on average. Final LifeASSURE™ BNA and BDA series cartridges achieved 2.1 million gallons throughput. Integrity was maintained throughout the test. |
| European Wine Producer/ Sweet White Wine | 16 x 30" cartridges 0.65 µm rated | Equal to better throughput compared to current filtration (current throughput ranges from 3000 hL to 10,000 hL depending on wine quality) Equal to better finished wine quality and microbial control. Current filtration scheme is a 2-stage system of lenticular depth pre-filter followed by a 0.65 µm alternative PES filter. Production flow rate = 90 hL/hr with filter change-outs every 2 to 3 months based on differential pressure or an integrity failure. | Successful first trial: 8,000 hL filtered; no microorganisms detected in finished wine. Integrity maintained after each hot water sanitation and citric acid cycle. Met expectations for finished wine quality. Successful second trial: 9,200 hL filtered, no microorganisms detected. Integrity maintained after hot water sanitization. Daily regeneration/sanitation: 20 minutes at 50°-55°C warm water followed by 20 minutes at 85°C hot water. |
| European Contract Mobile Wine Filtration/Red and White Wines | 5 x 20" cartridges 0.45 µm rated | Finished Wine Quality Eliminate concerns over current nylon membrane affecting the taste of finished wine. Confirm LifeASSURE™ BNA and BDA series membrane does not influence the taste of white wine, especially after steaming new filters after initial installation. | Trial conducted on a mobile filling line mounted on a truck. Finished wine quality unaltered. Aromatic composition of the finished wine unaffected by LifeASSURE™ BNA and BDA series filtration. Throughput target achieved. Filter integrity confirmed. |
| European Wine Producer/ Red and Rosé Wine | 8 x 30" cartridges 0.65 µm rated | Finished wine quality and microbial control. | Trial in-progress. Red and white wines filtered. 4070 hL filtered with ΔP only 0.2 bar. |
| European Wine Producer/ White Wine | 8 x 30" cartridges 0.45 µm rated | Finished wine quality and microbial control Surpass current throughput target of 4,600 hL achieved with alternate filter train. | LifeASSURE™ BNA and BDA series filters provided 12,800 hL throughput as compared to 4,600 hL throughput typically provided by the alternate filter. During the trial, the filters were exposed to 31 warm water (55°C)/hot water (90°C) regenerations plus 7 cold water/0.5% peracetic acid cycles. Turbidity after 3M Purification depth pre-filter = 1.5 NTU, after LifeASSURE™ BNA and BDA series = 0.4 NTU. Alternative pre-filters to alternative final filters only filtered 4200 hL. Second trial in-progress. Regeneration with NaOH and hot water (90°C) instead of peracetic acid hot water. Through 15 regeneration cycles, 4600 hL filtered with only a small increase in differential pressure. Test site reported that regeneration step using warm water (50° - 55°C) was very short (1 minute maximum.) |

Conclusions

- LifeASSURE™ BNA and BDA series cartridges utilize a robust cartridge design containing a highly asymmetric BNA and BDA series membrane.
- LifeASSURE BNA and BDA series filters are compatible with routine cleaning and sanitization procedures used in the Food & Beverage Industry, including multiple hot water and steam sanitization cycles, caustic cleaning agents and peracetic acid/peroxide sanitization agents.
- Laboratory testing demonstrates the membrane design is highly efficient for removal of spoilage organisms, yeast and secondary fermentation bacteria.
- LifeASSURE BNA and BDA series filters provide exceptional protection of finished wine, thus increasing shelf life by removal of spoilage organisms.
- The unique LifeASSURE BNA and BDA series cartridge design provides significantly longer service life for improved filtration economics.
- The excellent performance of LifeASSURE BNA and BDA series filters was proven through beta-site testing at commercial wineries in both the US and Europe.

Important Notice

The information described in this literature is accurate to the best of our knowledge. A variety of factors, however, can affect the performance of the product(s) in a particular application, some of which are uniquely within your knowledge and control. **INFORMATION IS SUPPLIED UPON THE CONDITION THAT THE PERSONS RECEIVING THE SAME WILL MAKE THEIR OWN DETERMINATION AS TO ITS SUITABILITY FOR THEIR USE. IN NO EVENT WILL 3M PURIFICATION INC. BE RESPONSIBLE FOR DAMAGES OF ANY NATURE WHATSOEVER RESULTING FROM THE USE OF OR RELIANCE UPON INFORMATION.**

It is your responsibility to determine if additional testing or information is required and if this product is fit for a particular purpose and suitable in your specific application.

3M PURIFICATION INC. MAKES NO REPRESENTATIONS OR WARRANTIES, EITHER EXPRESS OR IMPLIED, INCLUDING WITHOUT LIMITATION ANY WARRANTIES OF MERCHANTABILITY, FITNESS FOR A PARTICULAR PURPOSE OR OF ANY OTHER NATURE HEREUNDER WITH RESPECT TO INFORMATION OR THE PRODUCT TO WHICH INFORMATION REFERS.

Limitation of Liability

3M Purification Inc. will not be liable for any loss or damage arising from the use of the Product(s), whether direct, indirect, special, incidental, or consequential, regardless of the legal theory asserted, including warranty, contract, negligence or strict liability. Some states and countries do not allow the exclusion or limitation of incidental or consequential damages, so the above limitation may not apply to you.

**3M Purification Inc.**

400 Research Parkway
Meriden, CT 06450
U.S.A.
(800) 243-6894
(203) 237-5541
Fax (203) 630-4530
www.3mpurification.com

Your Local Distributor:

3M is a trademark of 3M Company.
LifeASSURE is a trademark of
3M company used under license.
© 2011 3M Company. All rights reserved.
Please recycle. Printed in U.S.A.
70-0201-8838-2 REV 1011b